



Adsorption of CO₂ on Zeolite 13X Prepared from Modified Natural Iranian Kaolin

V. Garshasbi¹, M. Jahangiri¹, M. Anbia^{2*}

¹Faculty of Oil, Gas and Chemical Engineering, Semnan University, Semnan, Iran

²Research Laboratory of Nanoporous Materials, Faculty of Chemistry, Iran University of Science and Technology, Farjam Street, Narmak, Tehran 16846-13114, Iran

PAPER INFO

Paper history:

Received 23 February 2016

Accepted in revised form 20 April 2016

Keywords:

Metakaolinization

Synthesized zeolite 13X

Adsorption

Carbon dioxide

Kaolinite

A B S T R A C T

Synthesis of zeolite 13X from modified natural Iranian kaolin at 65°C for 72 h at various concentration of NaOH solution was investigated. Metakaolinization process was done at 900°C for 2 h. NaOH solution with different concentrations, 1.0, 1.5, 2.0, 2.5, 3.0, 3.5 and 4 M were separately mixed with metakaolins. A mixture of zeolite 13X, A, quartz and hydroxysodalite (HS) was obtained. The products were characterized by X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FTIR) and scanning electron microscopy (SEM). The prepared zeolite 13X has been used to study the adsorption of carbon dioxide, and the results are compared with commercial zeolite 13X.

doi: 10.5829/idosi.ijee.2016.07.03.13

INTRODUCTION

CO₂ is contained in natural gas, atmosphere and exhaust gas in industrial processes [1]. There is a great challenge to decrease the concentration of carbon dioxide, because the amount of CO₂ in atmosphere globally increasing which leads to 55% rise in worldwide temperature [2, 3]. Adsorption of carbon dioxide by solid adsorbents, such as metal-organic frameworks (MOFs) [4, 5], alumina [6], carbons [7, 8] and zeolites based on physical or chemical adsorption processes, has been actively investigated [9].

Zeolites are nanoporous inorganic materials with different important applications, such as in catalysis, ion exchange and separations [2, 10-14]. Its frameworks are composed of [SiO₄]⁴⁻ and [AlO₄]⁵⁻ tetrahedra. Commonly, zeolites are synthesized from different sources of silica and alumina by hydrothermal treatment. To reduce the cost of synthetic zeolites, silica and alumina from chemical sources such as materials like bentonite [15], lithium slag [16], high silicon fly ash [17], paper sludge [18], bagasse fly ash [19], oil shale ash [20], coal fly ash [21], waste porcelain and kaolinite have been employed [22]. Al₂Si₂O₅(OH)₄ or kaolinite is a mineral clay that is consist of silica and alumina. For synthesis of

zeolite 13X from kaolinite the amount of Al must be decreased or Si increased [23] in order to obtain zeolite 13X, the ratio of Si/Al values must be above 1.5.

In this work, we have synthesized the 13X zeolite from modified natural Iranian kaolin by hydrothermal treatment. The effect of NaOH concentration (1.0, 1.5, 2.0, 2.5, 3.0, 3.5 and 4 M NaOH) was investigated and synthesized products were characterized by X-ray diffraction (XRD), scanning electron microscopy (SEM) and Fourier transform infrared (FTIR) spectroscopy. Finally, the adsorption of CO₂ on the synthesized zeolite 13X was investigated.

Material and Methods

Raw Materials

The natural kaolin (a source of silica and alumina) from Iranian sources was used for the present study. This kaolin had high amount of SiO₂ and low amount of Al₂O₃, so we modified it by acidizing to obtain convenient kaolin for synthesis of 13X zeolite. Table 1 shows the properties of raw kaolin and modified kaolin. Metakaolin was obtained by calcining kaolin in muffle furnace at 900°C for 2 h.

* Corresponding author: Mansoor Anbia

E-mail: anbia@iust.ac.ir; Tel: 0098 21 77240516; Fax: 0098 21 77491204

Synthesis Process

NaOH solutions with different concentrations, 1.0, 1.5, 2.0, 2.5, 3.0, 3.5 and 4 M were separately mixed with metakaolins. The samples were homogenized at room temperature for 20 min and then the reaction mixtures were distributed in autoclave. The autoclave was kept in a conventional air oven at 65°C for 72 h at autogenous pressure. The product was washed with deionized water to reach pH=9 and then dried at 90°C for 12 h.

TABLE 1. properties of natural kaolin before and after modification

composition	Content (%)	
	kaolin	Modified kaolin
SiO ₂	74.98	56.40
Al ₂ O ₃	17.42	31.68
Fe ₂ O ₃	0.54	0.26
TiO ₂	0.96	0.28
CaO	1.62	0.65
MgO	0.27	0.24
Na ₂ O ₃	1.04	0.31
K ₂ O	0.03	0.03
P ₂ O ₅	0.12	0.11
L.O.I	3.02	10.04

Characterization Techniques

Chemical composition of kaolin was determined by Bruker S4 wavelength X-ray dispersive fluorescence spectrometer (WDXRFS), with a Rh X-ray tube. The X-ray powder diffraction (XRD) patterns were recorded on a Philips PW1140/90 diffractometer using Cu-K α target (40 kV, 25 mA) at the scan rate of 2°/min and at 2 θ angles ranging from 5° to 80° with step size of 0.02°.

Infrared transmission spectra of the samples were made by the KBr wafer technique. The spectra were recorded on Fourier transform infrared spectrometer system 2000 FT-IR (Perkin-Elmer).

Scanning electron microscope (SEM) micrographs were taken with a JEOL JSM-6300F scanning electron (15 kV). The energy dispersive X-ray spectrometer (EDXS) attached to the SEM was used to conduct elemental analysis of samples.

RESULTS AND DISCUSSION

Characterization of Adsorbent

From Table 1, it is observed that the main constituents of the natural kaolin were silica (74.98%) and alumina (17.42%). After modification, these percentages were silica (56.40%) and alumina (31.68%). Fig. 1 shows the XRD pattern of metakaolin and natural kaolin. Kaolinite is identified by its characteristic X-ray diffraction peaks at 12.30° and 24.60° 2 θ that has been reported earlier [24]. The XRD pattern of metakaolin obtained by heating natural kaolin for 2h at 900°C resembled others, except for the peaks due to admixed impurities. XRD pattern

after heating shows a significant change in compare to the untreated kaolin pattern. Highest diffraction peaks are very common in metakaolin amorphous structure that corresponds to the presence of quartz.

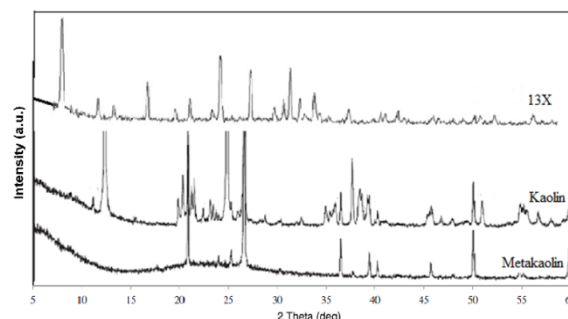


Figure 1. XRD pattern of kaolin, metakaolin and commercial zeolite 13X

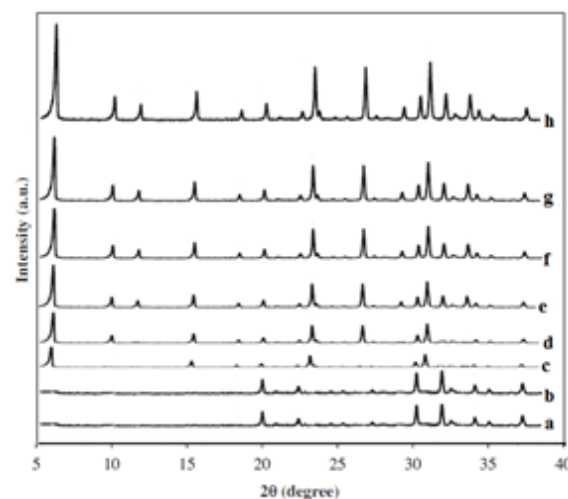


Figure 2. XRD pattern of zeolite 13X and associated phases obtained by hydrothermal synthesis: (a) 1.0 M NaOH, (b) 1.5 M NaOH, (c) 2.0 M NaOH, (d) 2.5 M NaOH, (e) 3.0 M NaOH, (f) 3.5 M NaOH, (g) 4.0 M NaOH, and (h) commercial zeolite 13X.

The XRD pattern of different products that is synthesized from different concentration of NaOH is shown in Fig. 2. The formation of synthesized zeolite 13X in the products was detected, by comparing its d-values with d-values of commercial zeolite 13X sample. The characteristic peaks of zeolite 13X are the most important change observed in the XRD patterns. The synthesized products matched the characteristic peaks of zeolite 13X at 2 θ values of 6.12°, 10.00°, 11.73°, 15.43°, 18.42°, 20.07°, 23.31°, 26.65°, 29.21°, 30.30°, 30.94°, 31.98°, 33.59° and 37.34°. Fig. 2a, 2c and 2d illustrates the XRD pattern of the product which was obtained from the sample with 1.0 M, 1.5 M and 2.0 M NaOH solution that has significant amount of metakaolin (amorphous) was observed. With increasing NaOH concentration the results indicated that the synthesized zeolite products obtained from 2.5–4.0 M

NaOH concentrations contain zeolite 13X as the major constituent phase.

Fig. 3 illustrates the IR spectra of different synthesized samples of zeolite 13X by reacted kaoline and commercial zeolite 13X. Spectrum a in Fig. 2 shows the broad band of metakaolin in the range from about 920 cm^{-1} to about 670 cm^{-1} and is assigned to Al-O bonds in Al_2O_3 . During the reaction between NaOH and metakaolin, SiO_2 and Al_2O_3 are transformed to aluminosilicates. Their vibration bands in the IR spectrum are replaced by a single band around 1000 cm^{-1} , characteristic of Si-O-Al bonds in TO_4 tetrahedral [24].

The appearances of the zeolite produced from metakaoline at various concentrations of NaOH is shown in SEM micrographs (Fig. 4). According to the experimental results of this work, the data obtained by SEM correlate and agree with the mineralogical composition of the zeolite products, which was determined through XRD results.

CO₂ Adsorption Isotherms

Fig. 5 shows the CO₂ adsorption isotherms of the zeolite 13X samples. 13X-M related to zeolite 13X that is produced from metakaolin and 13M-C is identified as commercial zeolite 13X. The 13X-M and 13X-C exhibited a CO₂ uptake of 255 and 265 mg/g, respectively; at 25°C and 20bar, whereas only 8mg/g was absorbed by kaolin. The high CO₂ uptake by zeolite 13X-C was attributed to its microporous structure with charge-compensating cations in the cavities [4]. The CO₂ capture capacities of 13X samples in this study were compared with different zeolites and several other CO₂ adsorbents reported in literature (Table 2).

TABLE 2. comparison of the CO₂ capture by different adsorbents

Sample	Adsorption temperature (°C)	CO ₂ uptake (mg/g)	Reference
13X-C	25	265	This work
13X-M	25	255	This work
Zeolite 13X	25	223	[25]
Zeolite 13X	25	211	[9]
Activated carbon	25	99	[7]
MCM-41	75	8.6	[26]
MOF-5	30	38	[27]

CONCLUSION

Synthesis of zeolite 13X from modified natural Iranian kaolin at 65°C for 72 h in various concentration of NaOH solutions is made. Metakaolin was obtained by calcining kaolin in muffle furnace at 900 °C for 2h. The zeolite 13X

that was produced by this process, was characterized by X-ray diffraction (XRD), Fourier transform infrared spectroscopy (FTIR) and scanning electron microscopy (SEM). All results are in good agreement with literatures.

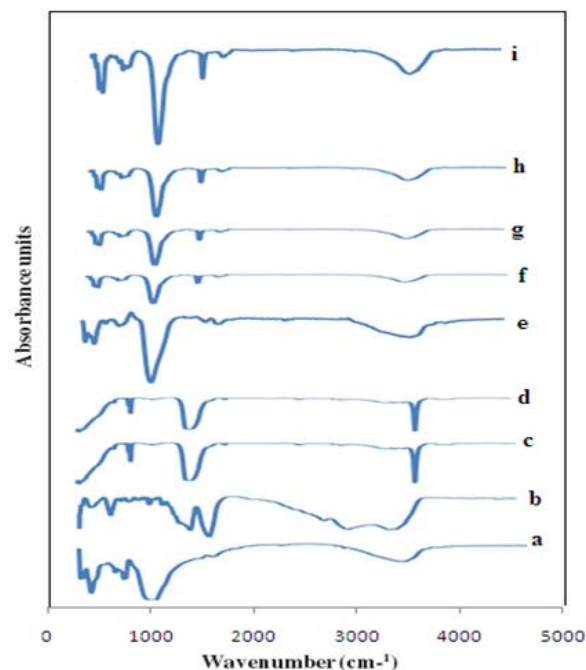


Figure 3. FTIR spectra of zeolite 13X and associated phases obtained by hydrothermal synthesis: (a) unreacted metakaolin, (b) 1.0 M NaOH, (c) 1.5 M NaOH, (d) 2.0 M NaOH, (e) 2.5 M NaOH, (f) 3.0 M NaOH, (g) 3.5 M NaOH, (h) 4.0 M NaOH, and (i) commercial zeolite 13X.

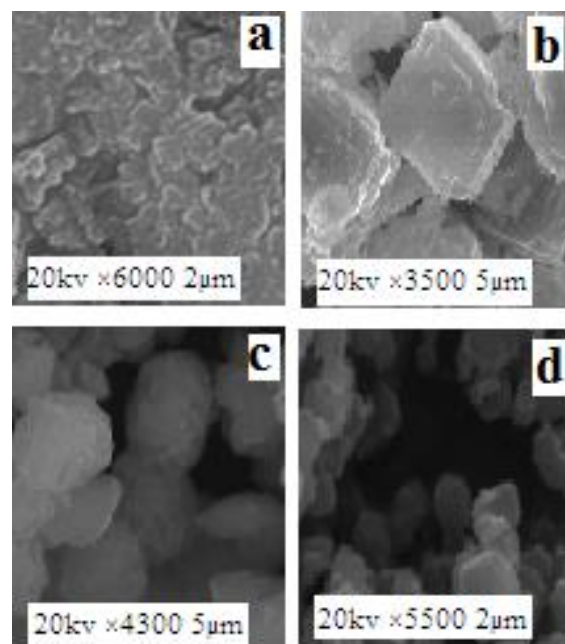


Figure 4. SEM micrographs of zeolite 13X crystals produced from metakaolin in NaOH concentrations a) 1.0M b) 2.0M c) 3.0M d) 4.0M

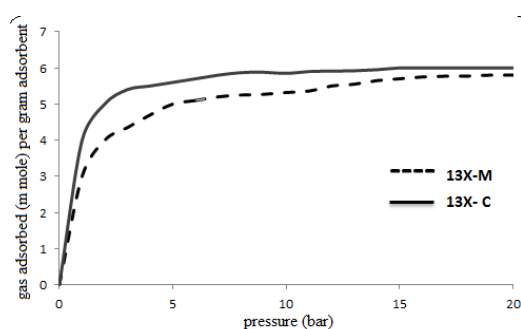


Figure 5. CO₂ adsorption by commercial zeolite 13X (13X-C) and zeolite 13X prepared by natural kaolin (13X-M)

REFERENCES

- Zhao, Z., Cui, X., Ma, J., Li, R., 2007. Adsorption of carbon dioxide on alkali-modified zeolite 13X adsorbents. *International Journal of Greenhouse Gas Control*. 1: 355-359.
- Lee, J.S., Kim, J.H., Kim, J.T., Suh, J.K., Lee, J.M., 2002. Adsorption equilibria of CO₂ on zeolite 13X and zeolite X/activated carbon composite. *Journal of Chemical Engineering Data*. 47: 1237-1242.
- Rege, S.U., Yang, R.T., Buzanowski, A.M., 2000. Sorbents for air pre-purification in air separation. *Chemical Engineering Science*. 55: 4827-4832.
- Millward, A.R., Yaghi, O.M., 2005. Metal-Organic Frameworks with Exceptionally High Capacity for Storage of Carbon Dioxide at Room Temperature. *Journal of American Chemical Society* 127: 7998-17999.
- Chen, C., Kim, J., Yang, D.A., Ahn, W.S., 2011. Carbon dioxide adsorption over zeolite-like metal organic frameworks (ZMOFs) having a sod topology: Structure and ion-exchange effect. *Chemical Engineering*. 168: 1134-1139.
- Chen, C., Ahn, W.S., 2011. CO₂ capture using mesoporous alumina prepared by a sol-gel process. *Chemical Engineering*. 166: 646-652.
- Chen, C., Kim, J., Ahn, W.S., 2012. Efficient carbon dioxide capture over a nitrogen-rich carbon having a hierarchical micropore structure. *Fuel*. 95: 360-364.
- Hao, G.P., Li, W.C., Qian, D., Lu, A.H., 2010. Rapid Synthesis of Nitrogen-Doped Porous Carbon Monolith for CO₂ Capture. *Advanced Materials*. 22: 853-857.
- Chen, C., Park, D.W., Ahn, W.S., 2014. CO₂ capture using zeolite 13X prepared from bentonite. *Applied Surface Science* 292: 63-68.
- Alshameri, A., Yan, C.J., Yasir, A.A., Ammar, S.D., Abdullateef, I., Zhao, C.Y., Wang, H.Q., 2014. An investigation into the adsorption removal of ammonium by salt activated Chinese (Hulaodu) natural zeolite: Kinetics, isotherms, and thermodynamics. *Journal of Taiwan Institute of Chemical Engineers* 45: 554-564.
- Tosheva, L., Vltchev, V.P., 2005. Nanozeolites: Synthesis, Crystallization Mechanism, and Applications. *Chemical Materials*. 17: 2494-2513.
- Cundy, C.S., Cox, P.A., 2003. The Hydrothermal Synthesis of Zeolites: History and Development from the Earliest Days to the Present Time. *Chemical Reviews*. 103: 663-701.
- Yan, Y., Bein, T., 1995. Zeolite Thin Films with Tunable Molecular Sieve Function. *Journal of American Chemical Society*, 117: 9990-9994.
- Kazemian, H., Modarress, H., Kazemi, M., Farhadi, F., 2009. Synthesis of submicron zeolite LTA particles from natural clinoptilolite and industrial grade chemicals using one stage procedure. *Powder Technology*. 196: 22-27.
- Ma, Y., Yan, C., Alshameri, A., Qiu, X., Zhao, C., Li, D., 2014. Synthesis and characterization of 13X zeolite from low-grade natural kaolin. *Advanced Powder Technology*. 25: 495-500.
- Chen, D., Hu, X., Shi, L., Cui, Q., Wang, H.Y., Yao, H.Q., 2012. Synthesis and characterization of zeolite X from lithium slag. *Applied Clay Science*. 59: 148-151.
- Kazemian, H., Naghdali, Z., Kashani, T.G., Farhadi, F., 2010. Conversion of high silicon fly ash to Na-P1 zeolite: alkaline fusion followed by hydrothermal crystallization. *Advanced Powder Technology*. 21: 279-284.
- Wajima, T., Haga, M., Kuzawa, K., Ishimoto, H., Tamada, O., Ito, K., Nishiyama, T., Downs, R.T., Pakovan, J.F., 2006. Zeolite synthesis from paper sludge ash at low temperature (90 °C) with addition of diatomite. *Journal of Hazardous Materials*. 132: 244-252.
- Pornomo, C.W., Salim, C., Hinode, H., 2012. Synthesis of pure Na-X and Na-A zeolite from bagasse fly ash. *Microporous and Mesoporous Materials*. 162: 6-13.
- Machado, N.R.C.F., Miotto, D.M.M., 2005. Synthesis of Na-A and -X zeolites from oil shale ash. *Fuel*. 84: 2289-2294.
- Tanaka, H., Fujii, A., 2009. Effect of stirring on the dissolution of coal fly ash and synthesis of pure-form Na-A and -X zeolites by two-step process. *Advanced Powder Technology*. 20: 473-479.
- Colina, F.G., Liorens, J., 2007. Study of the dissolution of dealuminated kaolin in synthesis. *Microporous and Mesoporous Materials*, 100: 302-306.
- Colina, F.G., Esplugas, S., Costa, J., 2002. High-Temperature Reaction of Kaolin with Sulfuric Acid. *Industrial & Engineering Chemistry Research*. 41: 4168-4173.
- Gougazeh, M., Buhl, J.C., 2013. Synthesis and characterization of zeolite A by hydrothermal transformation of natural jordanian kaolin. *JAAUBAS* 15: 35-41.
- Cavenati, S., Grande, C.A., Rodrigues, A.E., 2004. Adsorption equilibrium of methane, carbon dioxide, and nitrogen on zeolite 13X at high pressure. *Journal of Chemical Engineering* 49: 1095-1099.
- Xu, X., Song, C., Andresen, J.M., Miller, B.G., Scaroni, A.W., 2003. Preparation and characterization of novel CO₂ molecular basket adsorbents based on polymer-modified mesoporous molecular sieve MCM-41. *Microporous and Mesoporous Materials*. 62: 29-34.
- Lu, C.M., Liu, J., Xiao, K., Harris, A.T., 2010. Microwave enhanced synthesis of MOF-5 and its CO₂ capture ability at moderate temperatures across multiple capture and release cycles. *Chemical Engineering Journal*. 156: 465-470.

Persian Abstract

DOI: 10.5829/idosi.ijee.2016.07.03.13

چکیده

سنتر زئولیت 13X از کائولین طبیعی ایرانی در دمای ۶۵ درجه سانتی گراد به مدت ۷۲ ساعت در غلظت های مختلف محلول سود مورد بررسی قرار گرفت. فرآیند متاکائولیزاسیون در دمای ۹۰۰ درجه سانتی گراد به مدت ۲ ساعت انجام شد. محلول سود با غلظت های ۱، ۱.۵، ۲، ۲.۵، ۳، ۳.۵ و ۴ مولار با متاکائولین مخلوط شد. مخلوطی از زئولیت 13X و کوآتز و هیدروکسی سودالیت بدست آمد. مشخصات محصول با آزمایش های FT-IR، XRD و SEM مورد بررسی قرار گرفت. محصول تولید شده برای جذب دی اکسید کربن مورد استفاده قرار گرفت و نتایج با زئولیت طبیعی مقایسه شد.