



## Activated Carbon from Fenugreek Seed: Characterization and Adsorption Properties for Dye Removal

D. Basrur and J. Ishwara Bhat\*

Department of Chemistry, Mangalore University, Mangalagangothri-574199, Karnataka State, India

### PAPER INFO

#### Paper history:

Received 31 August 2017

Accepted in revised form 30 October 2017

#### Keywords:

Activated carbon

Adsorption

Kinetic parameters

Thermodynamic parameters

### ABSTRACT

In this work, the preparation of activated carbons from agricultural product, the fenugreek seeds by two approaches, chemical and microwave activation methods were studied. The characterization of carbon materials were carried out using different techniques such as Fourier Transform Infrared Spectroscopy (FTIR), Scanning Electron Microscopy (SEM), Thermo Gravimetric Analysis (TGA), X-Ray Diffraction (XRD). Adsorption experiment was carried out for the adsorption of two different basic dyes, Methylene Blue (MB) and Crystal Violet (CV) under varying conditions such as concentration, agitation time and temperature. The data acquired from concentration variation were found to fit well with Langmuir and also Freundlich isotherms. Kinetic studies revealed the fact that the system followed second order adsorption rate. Thermodynamic parameters such as  $\Delta H^\circ$ ,  $\Delta S^\circ$  and  $\Delta G^\circ$  were calculated from the obtained data on adsorption at different temperature.

doi: 10.5829/ijee.2017.08.03.03

### INTRODUCTION

Adsorption, a surface phenomenon occurs in most of the physical, biological and chemical systems. The term adsorption refers to the existence of a higher concentration of any particular component at the surface of a liquid or solid phase than is present in the bulk [1, 2]. Adsorption has many applications in industries particularly in decolourisation, drying gas, catalysis, water softening [3] etc. Activated carbon is the most widely used adsorbent around the world with application in diverse areas due to its adsorption capacity, variable surface chemistry characteristics and high chemical resistance [4]. Adsorption of organic substances by activated carbon results in specific interactions between functional group on the adsorbent and on the surface of the adsorbents [5]. This distinctive feature makes activated carbon as an excellent adsorbent in food industry, pharmaceutical, chemical, petroleum, nuclear, automobile and vacuum industries. These are also used for removal of organic pollutant like phenols [6], metal ions from water [7], decolourization [8], dechlorination [9], filtration of gases and liquids [10-12] etc. Physical and chemical activation are the two most extensively used methods for the synthesis of activated carbon. These days microwave heating technology emerging as a promising method in the production of activated carbon,

owing to the fact that this method is very effective compared to other methods [13, 14].

Consumption of refined sugar (refined from bone char) or direct ingestion of activated carbon (made from wood, coir husk and fossil fuels etc) in the form of dietary supplement may lead to serious health problems. Therefore, work on agricultural related charcoal has been carried out which could be an alternative to commercial carbon. In this study fenugreek seed, an agricultural product which is cheap and abundant was used as raw material for the preparation of activated carbon. Fenugreek (*Trigonella foenum - graecum*) is belong to family *fabaceae*. Fenugreek seeds (Figure 1) are yellow-brown coloured which are mainly used for food and medicinal uses. The chemical constituent of fenugreek seed are proteins, amino acids, fatty acids, flavonoids, alkaloids, carbohydrates, saponins, sapogenins, fibres etc [15-18]. The study includes the preparation of activated carbon by two methods namely, chemical activation and microwave treatment and its characterization. The prepared carbons were used as an adsorbent for the study of adsorption of methylene blue and crystal violet. Validations of two adsorption isotherms such as Freundlich and Langmuir isotherm were studied. In addition, to know the feasibility of the reaction, thermodynamic parameters evaluation was also carried out.

\* Corresponding author: Ishwara Bhat  
E-mail: bhatij@yahoo.com



Figure 1. Fenugreek seed

## MATERIAL AND METHODS

All chemical reagents used in the experiments were of analytical grade.

### Preparation of activated carbon

The fenugreek seeds were washed with water to remove dirt and dust. Later it was dried in an oven at 110°C. Two step activation procedure was adopted for chemical activation method. Firstly fenugreek seed powder was pre-carbonized at 250°C for 2 hours in a hot air oven. The pre-carbonized sample was treated with 10% ZnCl<sub>2</sub> solution and agitated on a hot plate at 60°C for one hour. Later it was filtered, dried; carbonization was carried at 400°C for one hour in a muffle furnace. The sample obtained was washed with hot water as well as distilled water to eliminate remnant impurities, dried in an oven at 110°C and resulted activated carbon is designated as ZFC. Microwave treatment was carried out in a domestic microwave oven. The input power of the microwave oven was set at 90 W (Energy ≈ 270 joules/s). The sample was irradiated for 3 hours and the obtained carbon was labelled as MFC.

### Characterization of activated carbon

Fourier Transform Infrared spectrum of activated carbon was recorded over the frequency range of 4000 to 400 cm<sup>-1</sup> using IR Prestige-21 Fourier Transform infrared spectrometer, Shimadzu (Japan). Thermogravimetric study was carried out using the instrument SDT Q600 V20.9 (Japan) at a heating rate of 10°C/min under a nitrogen flow of 10ml/min. X - Ray Diffraction study was performed by Rigaku Miniflex 600 (Japan). Scanning Electron Micrographs were obtained using Sigma Series Field Emission Scanning Electron Microscope (Zeiss, Germany).

### Adsorption studies

Prepared activated carbons (ZFC and MFC) were used as an adsorbent for the adsorption of two dyes, methylene

blue and crystal violet under varying conditions such as temperature, agitation time and concentration of the dye. For the adsorption studies, a definite amount of adsorbent of particle size 50-100 micron was added to a 250-ml conical flask containing 50 ml of the dye solution and agitated for fixed time span. Later the dye solution was filtered and its concentration was determined spectrophotometrically by observing corresponding  $\lambda_{\max}$  values (664nm for Methylene Blue and 588nm for Crystal Violet). The amount of methylene blue adsorbed,  $q_e$  (mg/g), by carbon at time  $t$ , was calculated by the following equation:

$$q_e = \frac{(C_o - C_e)V}{W} \quad (1)$$

where  $C_o$  and  $C_e$  are initial and equilibrium concentration (mg/l),  $V$  is volume of solution(l) and  $W$  is the weight of activated carbon (g).

## RESULTS AND DISCUSSION

### Characterization of activated carbon


#### FTIR analysis

The functional groups present on activated carbon were identified by the observed peaks in an FTIR spectrum obtained for activated carbons. The FTIR spectrum obtained for raw fenugreek seed (RFS) powder and prepared activated carbons (MFC and ZFC) are shown in Fig. 2. The absorption bands for activated carbons are listed in Table 1 with their structural assignments.

The broad but intense peak in the range 3400 - 3300 cm<sup>-1</sup> may be due to conjunction of O-H and N-H stretching. The bands at 2927.41 cm<sup>-1</sup> and 2854.13 cm<sup>-1</sup> are attributed to the asymmetric and symmetric stretching of C-H bonds respectively. The peak formed at 1745.26 cm<sup>-1</sup> is due to C=O stretch for esters. The bands at 1650.76 cm<sup>-1</sup> and 1540.84 cm<sup>-1</sup> indicates N-H bending of primary amines and secondary amines respectively. The weak bands occurred at 1454.06 cm<sup>-1</sup> may be the result of vibrations of C-O-H bonds. The band formed at 1398.13 cm<sup>-1</sup> may be due to bending mode of CH<sub>2</sub> groups. The band at 1240 cm<sup>-1</sup> is due to C-N stretching in amines and the band at 1068.37 cm<sup>-1</sup> may be due to C-O stretching of saponins.

A notable difference was observed when the study was further extended to correlate the spectra of both the raw fenugreek seed powder and the synthesised activated carbons. The peaks which are accountable for vibrations of N-H, O-H, C-H, C-O-H and C-O bonds are retained in the spectra of both MFC and ZFC where as the bands which are responsible for carbonyl stretching, N-H bending (Secondary amines) and C-N stretching are absent in the spectrum of activated carbons (MFC and

ZFC). The disappearance of bands may be attributed to the release of CO<sub>2</sub> by carbonyl group and decomposition of C–N bond, at higher temperature (400°C). MFC and

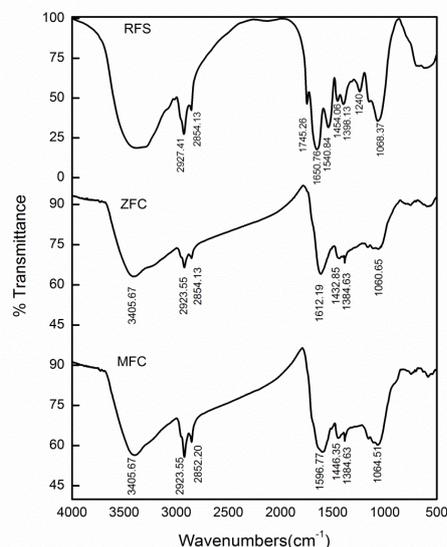

**Figure 2.** FTIR spectrum of raw fenugreek seed and activated carbon (ZFC &MFC)

ZFC showed similar spectrum with varied intensities and this variation in intensities may be due to impregnation of activated carbon with zinc chloride. El-Bahy [19] studied the composition of fenugreek seeds through FTIR and FT Raman spectra measurements. The obtained FTIR frequency,  $\nu$  values are well compared (Table 1). Peaks present in IR spectra indicated the presence of hetero atoms (N, O) and some  $\pi$  bonds on the surface of activated carbon, and they are believed to be are very active towards the adsorption process and hence the prepared carbons can be used as adsorbents.

**TABLE 1.** Spectrum assignment of fenugreek seed and synthesised activated carbons

RFS	MFC	ZFC	Assignment
3400-3300	3405.67	3417.24	N–H stretching, O–H stretching
2927.41	2923.55	2923.55	Asymmetrical –CH <sub>2</sub> - stretching
2854.13	2852.20	2854.13	Symmetric –CH <sub>2</sub> - stretching
1745.26	-	-	C=O stretching
1650.76	1596.77	1612.19	N–H bending (primary amines)
1540.84	-	-	N–H bending (Secondary amines)
1454.06	1446.35	1432.85	C–O–H bending
1398.13	1384.63	1384.63	(C–H <sub>2</sub> ) bending
1240.00	-	-	C–N stretching in amines
1068.37	1068.37	1060.65	C–O stretching

**XRD analysis**

The crystallographic characters of the raw sample and activated carbon were analysed by XRD with Cu-K $\alpha$  radiation. The XRD pattern obtained is shown in Fig. 3. Considerable difference was noticed in the obtained XRD patterns. Raw seed sample exhibited amorphous state where as few peaks were spotted in the X-ray

patterns of activated carbon and the difference in the XRD patterns could be due to the activation process. Presence of few sharp peaks in the midst of some weak peaks confirms that the activated carbons exhibit most likely, a mixture of single crystal and mixture of crystallites. Based on the intensity of existing peaks and  $2\theta$  values inter-planar distance  $d$ ,  $hkl$  values and cell volume,  $a^3$  were determined and obtained data are shown in Table 2. The interlayer spacing  $d$  is determined by using Bragg’s equation:

$$d = \frac{\lambda}{2\text{Sin}\theta} \tag{2}$$

where  $\lambda = 1.5418 \text{ \AA}$  (CuK $\alpha$ ) and  $\theta$  is the scattering angle. The value of ‘ $a$ ’ (Table 2) appears to be the same at different  $\theta$  values which indicates the cubic pattern for the system. The crystallite size  $D$ , was determined from the Scherrer equation:

$$D = \frac{K\lambda}{B \text{cos}\theta} \tag{3}$$

where  $K$  is the Scherrer constant value from 0.9 to 1,  $\lambda$  is the wavelength of the X – ray radiation and  $B$  is the width at half maximum [20]. Among the two synthesised carbons (Table 2) the higher cell volume and lower crystallite size of ZFC indicates likely higher adsorption capacity compared to MFC.


**TABLE 2.** XRD data for MFC and ZFC

Sample	$2\theta$ (degree)	$d$ (Å)	N	hkl	$a$ (Å)	Cell volume (Å) <sup>3</sup>	Crystallite size D(Å)
MFC	19.74	4.51	1	100	4.51	91.73	0.075
	20.88	4.27	1	100	4.27	77.85	0.075
	21.00	4.24	1	100	4.24	76.76	0.075
	21.55	4.14	1	100	4.14	71.47	0.075
	21.82	4.08	1	100	4.08	68.41	0.075
	22.44	3.97	1	100	3.97	63.04	0.075
	24.06	3.71	1	100	3.71	51.06	0.076
	28.06	3.19	2	110	4.51	91.73	0.076
	40.30	2.24	4	200	4.49	90.51	0.079
	ZFC	17.56	5.07	1	100	5.07	130.47
23.02		3.87	2	110	5.48	165.06	0.067
24.32		3.67	2	110	5.19	140.30	0.067
25.1		3.56	2	110	5.03	127.82	0.067
26.16		3.42	2	110	4.83	113.37	0.067


**Thermo gravimetric analysis**

The TG curve of raw fenugreek seed (RFS), MFC and ZFC obtained and are shown in Fig. 4. A considerable difference was observed in the pyrolysis behaviour of the raw fenugreek seed and synthesised activated carbons (MFC and ZFC). Weight loss in the range 20 - 200°C was the result of evaporation of moisture or loosely bound water molecules. RFS showed rapid degradation in the range 200-500°C which slowed down there after, whereas steady decomposition was observed for MFC (200 -700 °C) and ZFC (200- 800 °C). Decrease in mass beyond 200°C may be due the loss of water of crystallization or degradation of sapogenins, alkaloids and fibers present in the activated carbon. Retaining of the weight till about 500°C and later decrease probably

indicates the increase in the pores in the activated carbon which helps in the increase of adsorption.

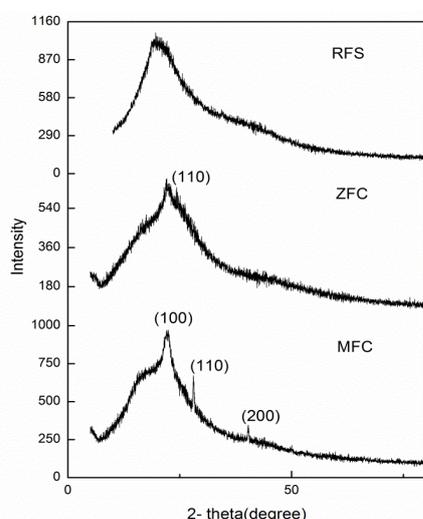

**Figure 3.** XRD of RFS and activated carbon (ZFC and MFC)

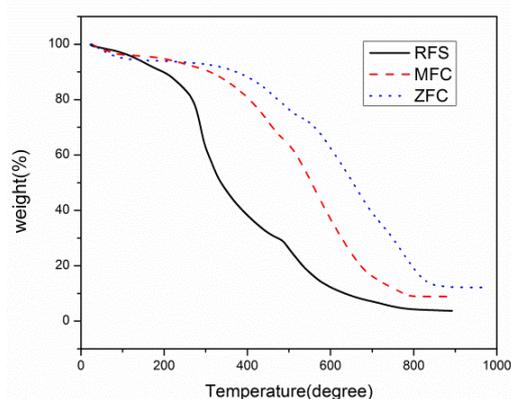

**Figure 4.** Thermogravimetric curve of RFS, MFC and ZFC

### Scanning electron microscopic (SEM) analysis

Surface morphologies, before and after adsorption were examined by SEM. Figs. 5a and 5b shows the scanning electron micrographs of MFC and ZFC respectively. It is evident from the images that both the carbon shows different surface structure and occurrence of large number of cavities, which plays key role in the process of adsorption. Figs. 5c, 5d, 5e, 5f are the post adsorption images; indicate blocking the surface cavities by the dye molecules. That is to say the interaction between the dye and the active centres of the carbon has taken place.

Characterization study indicates that the activated carbon prepared in the present study is a good adsorbent. Hence the adsorption study was carried out.

### Adsorption studies

#### Adsorption isotherms

Langmuir and Freundlich adsorption isotherm models were employed to describe the adsorption process. The linear form of the Freundlich Isotherm is given as [21]

$$\log q_e = \log K_f + \frac{1}{n} \log C_e \quad (4)$$

where  $n$  shows the adsorption intensity in the Freundlich equation and  $K_f$  is the Freundlich adsorption capacity [(mol/g)(L/g)<sup>1/n</sup>]. The values of  $n$  and  $K_f$  were calculated by the slope and intercept obtained from the plot of  $\log q_e$  vs.  $\log C_e$  (Figs. 6(a) and 6(b))

The Langmuir equation is expressed by the following expression [22].

$$\frac{C_e}{q_e} = \frac{1}{Q_o b} + \frac{C_e}{Q_o} \quad (5)$$

where  $C_e$ (mg/L) is the equilibrium concentration of the solute,  $q_e$  is amount of solute adsorbed at equilibrium(mg/g) and  $Q_o$ (mg/g) and  $b$ (L/mg) are constants related to the adsorption capacity and energy of adsorption respectively. The values of  $Q_o$  and  $b$  were calculated from the slope and intercept from the plot of  $C_e/q_e$  vs.  $C_e$ . ( Figs. 7(a) and 7(b)). The separation factor,  $R_L$  is calculated as:


$$R_L = \frac{1}{1 + bC_0} \quad (6)$$

where  $C_0$  is the initial concentration of the adsorbate.  $R_L$  value shows the form of the isotherm to be either linear ( $R_L=1$ ), irreversible ( $R_L= 0$ ), favourable ( $0 < R_L < 1$ ) or unfavourable ( $R_L > 1$ ) [23].

The results (Table 3) indicate that both the Langmuir and Freundlich models are equally applicable for the present system.  $R_L$  values lies between 0 and 1, implies that the adsorption process is favourable and also the values of  $n$  ( $>1$ ) are supportive to the adsorption process.

#### Effect of contact time

The variation in the adsorption of the dyes with contact time (15 – 120 min) is shown in Fig. 8. The result signifies the sharp increase in adsorption in the beginning (from 15-60 min) with later decline (from 60 – 120 min). In the initial stage, rate of adsorption is high due to availability of the active sites on the surface of the adsorbent. The maximum adsorption is found to be at 60 minutes for both the dyes. After 60 minutes the decrease in the adsorption is likely to be due to scarcity of vacant sites on the adsorbent. So the adsorption appears to decrease and it continued till the end of the study. Rate of adsorption appear to be more in case of ZFC than MFC for both the dyes.

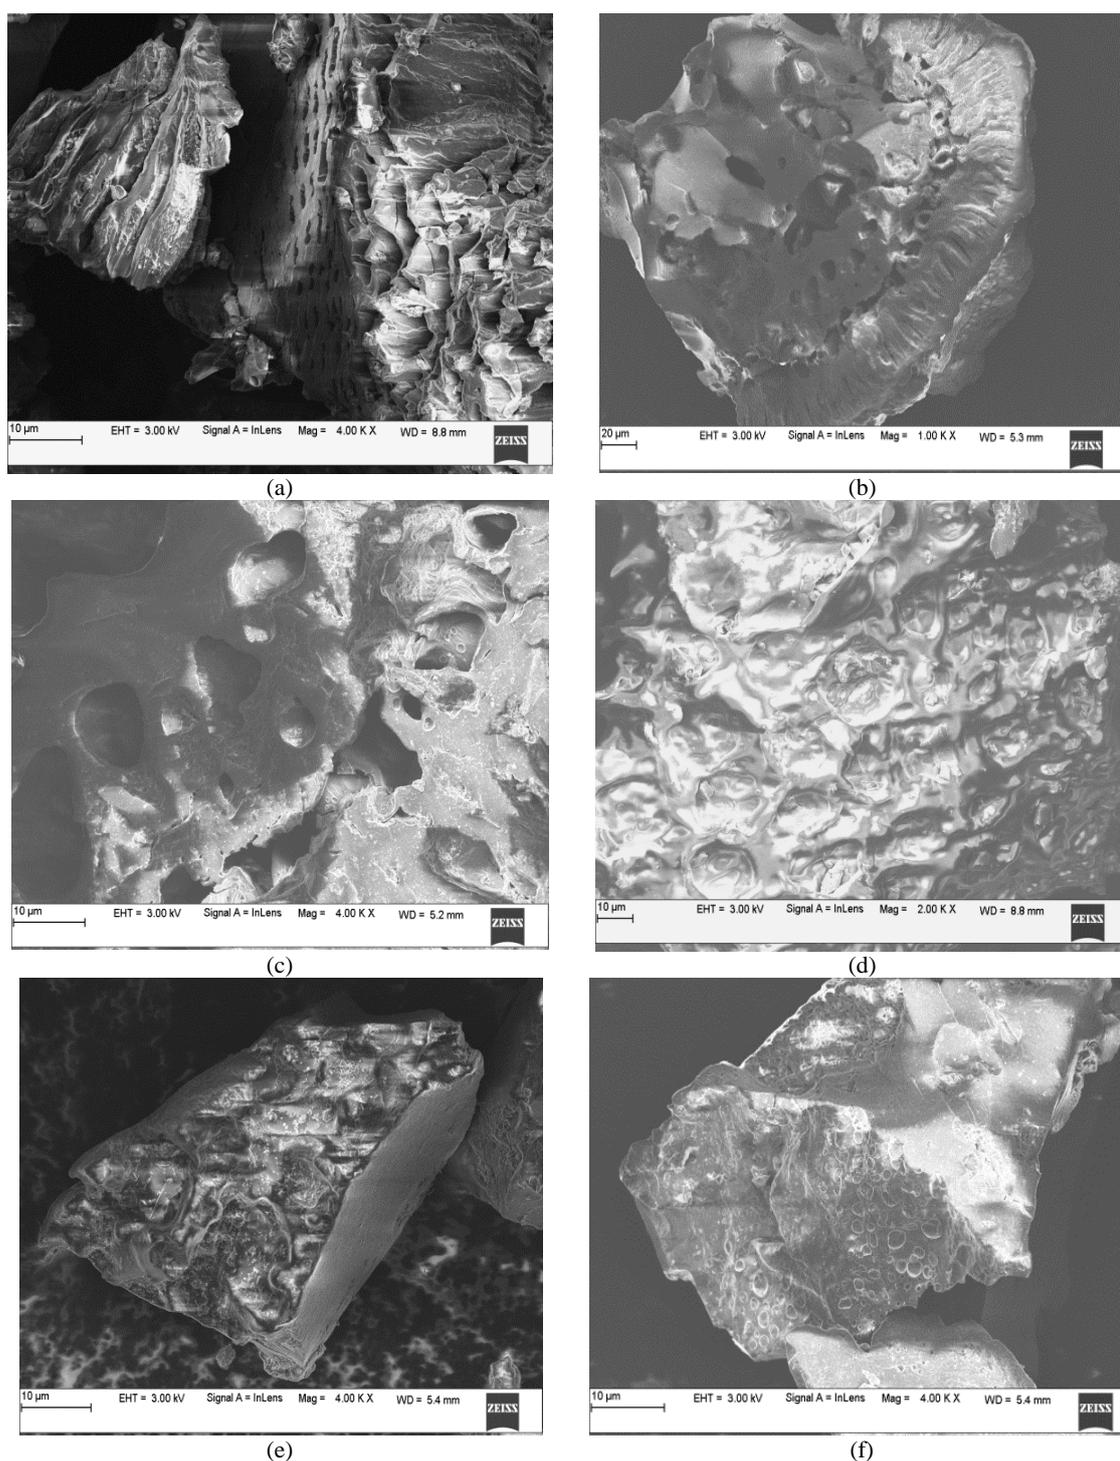

**Figure 5.** Scanning electron micrographs of activated carbon (a), (b) ZFC and MFC before adsorption, (c) ZFC after adsorption of MB, (d) MFC after adsorption of MB, (e) ZFC after adsorption of CV, (f) MFC after adsorption of CV.

**Table 3** Langmuir and Freundlich isotherm constants and correlation coefficients for adsorption capacity

Sample	Dye	Freundlich Isotherm			Langmuir Isotherm			
		$n$	$K_f$	$R^2$	$Q_o$	$b$	$R_L$	$R^2$
MFC	MB	2.20	2.28	0.98	35.08	0.13	0.27 - 0.07	0.99
	CV	2.53	2.54	0.97	37.39	0.17	0.21 - 0.05	0.98
ZFC	MB	1.56	2.12	0.97	64.43	0.06	0.42 - 0.13	0.97
	CV	1.46	1.89	0.97	64.64	0.05	0.48 - 0.15	0.99

**Adsorption kinetics**


In this investigation, the adsorption mechanism was studied by fitting first and second order rate expression to the experimental data. The first order kinetic model can be expressed as follows [24]:

$$\ln(q_e - q_t) = \ln q_e - k_1 t \tag{7}$$


where  $k_1$  is the equilibrium rate constant of the first order adsorption, and  $q_e$  and  $q_t$  refer to amount of dye adsorbed (mg/g) at equilibrium and at any time,  $t$  (min), respectively. The data obtained in this experimental work, did not fit well for the first order model. The linear form of the second - order kinetic model is represented as follows [25]:

$$\frac{t}{q_t} = \frac{1}{k_2 q_e^2} + \frac{t}{q_e} \tag{8}$$

where  $q_e$  and  $q_t$  are the adsorption capacities at equilibrium and time  $t$  respectively and  $k_2$  is the second order rate constant for adsorption ((mg/L)<sup>-1</sup> min<sup>-1</sup>). The rate constant  $k_2$  and  $q_e$  were computed respectively from the intercept and slope of the linear plot of  $t/q_t$  vs.  $t$  (Fig 9). The value of  $R^2$  (Table 4) confirms that second - order kinetic model fits best for the adsorption process.

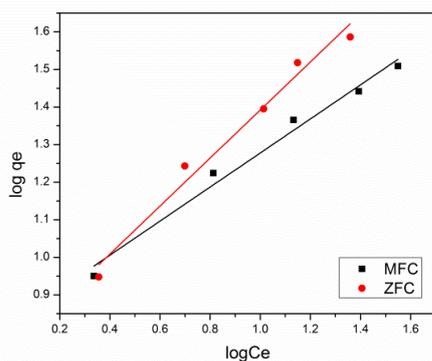

(a)

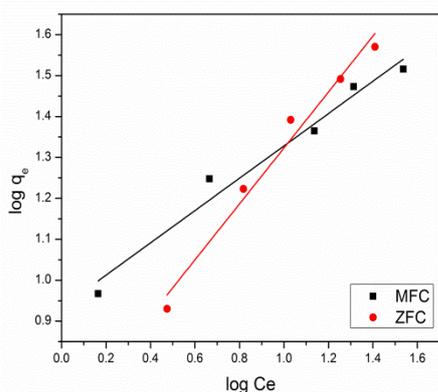


(b)

**Figure 6.** (a) Freundlich Isotherm for MB adsorption (b) Freundlich Isotherm for CV adsorption


**Effect of temperature**

Effect of temperature on the adsorption was carried out in the temperature range 20 – 70°C. The result indicated

that with the increase in temperature there is increase in the adsorption capacity of the carbon up to a certain temperature (50°C) with a later decrease in adsorption (Fig. 10). Increase in the adsorption capacity may be due to increase in the mobility of the dye molecules with an increase in their kinetic energy as well as increase in the pore volume of an adsorbent [26]. The decrease in adsorption capacity with increase in temperature is due to weakening of the intermolecular attractive forces between the active sites on the adsorbent and dye molecules, and also between the adjoining dye molecules on the adsorbed phase [27].

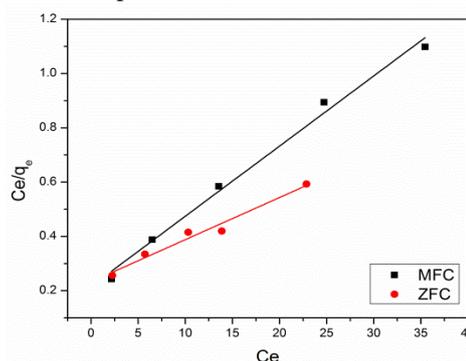


(a)

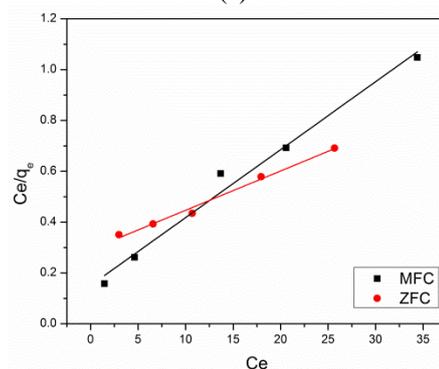

(b)

**Figure 7.** (a) Langmuir Isotherm for MB adsorption (b) Langmuir Isotherm for CV adsorption

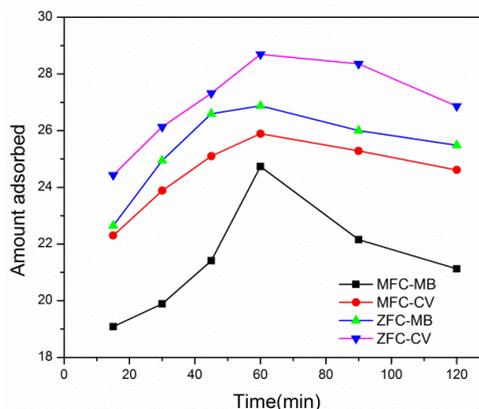

**Figure 8.** Effect of contact time for MB and CV adsorption

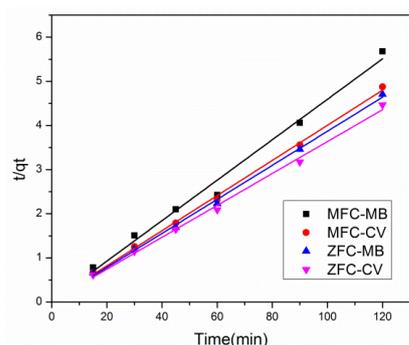


Figure 9. Plot of second – order kinetic modelling of the adsorption process

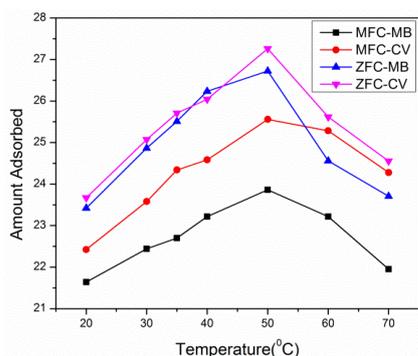


Figure 10. Effect of temperature for MB and CV adsorption

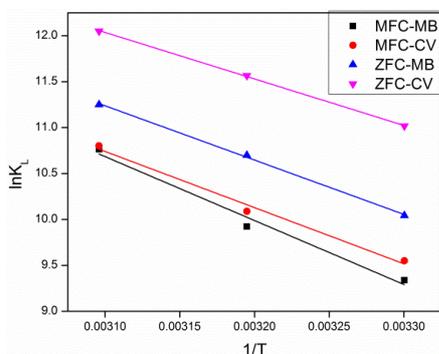


Figure 11. van't Hoff equation for MB and CV adsorption

**Adsorption thermodynamic**

From the study on the variation of temperature (30 - 50 °C), thermodynamic parameters  $\Delta H^\ddagger$ ,  $\Delta S^\ddagger$  and  $\Delta G^\ddagger$ , for the adsorption were calculated. For a dilute solution of charged adsorbate,  $\Delta G^\ddagger$  can be determined by using Langmuir equilibrium constant [28, 29]:

$$q_e = q_{max} \frac{C_e K_L}{C_e K_L + 1} \tag{9}$$

where  $q_e$  and  $q_{max}$  are the adsorption capacity of adsorbent at equilibrium (milligrams per gram) and its maximum value,  $C_e$  is the equilibrium concentration of adsorbate in solution (moles/l) and  $K_L$  is the Langmuir equilibrium constant of adsorption (litres per mole). Change in free energy,  $\Delta G^\ddagger$  is calculated as

$$\Delta G^\ddagger = -RT \ln K_L \tag{10}$$

where  $R$  is the gas constant,  $T$  is the absolute temperature. Enthalpy and entropy of the adsorption process can be calculated from the van't Hoff equation:

$$\ln K = \frac{-\Delta H^\ddagger}{RT} + \frac{\Delta S^\ddagger}{R} \tag{11}$$

Activation Energy,  $E_a$  was determined by using the following equation:

$$E_a = \Delta H^\ddagger + RT \tag{12}$$

The values of  $\Delta H^\ddagger$  and  $\Delta S^\ddagger$  were calculated from the slope and intercept of the linear plot of  $\ln K$  vs.  $1/T$  (Fig. 11) and the results obtained are given in Table 5.

Positive values of  $\Delta H^\ddagger$  and  $E_a$  indicate that the adsorption is an endothermic process and absorb necessary energy from the surroundings. The low values of  $\Delta H^\ddagger$  also specifies that the system experiences physisorption. Negative value of  $\Delta G^\ddagger$  indicates the spontaneous nature

**Table 4** Second order rate constants for the adsorption

Sample	Dye	$q_e$	$k_2$	$R^2$
MFC	MB	21.82	0.184	0.99
	CV	25.12	0.065	0.99
ZFC	MB	25.92	0.122	0.99
	CV	27.67	0.059	0.99

**Table 5** Thermodynamic parameters for the Adsorption of MB and CV on activated carbon

Sample	Dye	Temperature (°C)	$K_L$ (L/mol)	$\Delta G^\ddagger$ (kJ/mol)	$\Delta H^\ddagger$ (kJ/mol)	$\Delta S^\ddagger$ (kJ/mol /K)	$E_a$ (kJ/mol)
MFC	MB	30	11.36 x10 <sup>3</sup>	- 23.52	57.87	0.268	60.39
		40	20.41 x10 <sup>3</sup>	- 25.82			
		50	47.29 x10 <sup>3</sup>	- 28.90			
	CV	30	14.04 x10 <sup>3</sup>	- 24.05			
		40	24.04 x10 <sup>3</sup>	- 26.25			
		50	49.15 x10 <sup>3</sup>	- 29.01			
ZFC	MB	30	22.98 x10 <sup>3</sup>	- 25.29	49.15	0.245	51.75
		40	44.33 x10 <sup>3</sup>	- 27.84			
		50	76.88 x10 <sup>3</sup>	- 30.21			
	CV	30	60.88 x10 <sup>3</sup>	- 27.75			
		40	10.55 x10 <sup>4</sup>	- 30.09			
		50	17.13 x10 <sup>4</sup>	- 32.36			

of adsorption, which decreased with the increase in temperature. The change in  $\Delta G^\ddagger$  with temperature suggests that adsorption is a favourable process and the positive values of  $\Delta S^\ddagger$  state the involvement of slight disorderliness in the adsorption process.

## CONCLUSION

Activated carbons were prepared from fenugreek seed, characterized by FTIR, XRD, SEM and TGA, and utilized for adsorption study. Results from the concentration variation indicated that both Langmuir and Freundlich Isotherm models could be used to fit the data. Kinetic studies revealed that the system follows second order rate. Thermodynamic parameters were calculated and the adsorption process was found to be endothermic and spontaneous.

## Acknowledgement

The authors are thankful to the Coordinator, DST-FIST programme, USIC and DST-PURSE, Mangalore University for providing instrumental facilities. The authors are also thankful to UGC-SAP, Delhi for financial assistance to carry out the present research work.

## REFERENCES

- J.C. Kuriacose, J Rajaram, 1988. Chemistry in Engineering and Technology. Tata McGraw- Hill Publishing Company Limited, New Delhi.
- Clair N. Sawyer, Perry L. McCarty, Gene F. Parkin, 1994. Chemistry for Environmental Engineering, McGraw- Hill international Editions, Singapore.
- Gurudeep Raj, 1991. Surface Chemistry (Adsorption), Goel Publishing House, Meerut.
- Yuhui Ma, Qunhui Wang, Xiona Wang, Xiaohong Sun, Xiaoqiang Wang, 2015. A Comprehensive study on activated carbon prepared from spent Shiitake substrate via pyrolysis with  $ZnCl_2$ . J Porous Mater 22(1): 157 – 169.
- Walter J. Weber JR 1973. Adsorption Processes. XXIVth International Congress of Pure and Applied chemistry, Symposium S2, Hamburg, pp: 375-392
- C R Girish and V. Ramachandra Murty, 2012. Adsorption of phenol from aqueous solution using Lantana Camara, Forest Waste: Kinetics, Isotherm and Thermodynamic Studies. Journal of Environmental Research and Development 6: 763-772.
- Rifaqat Ali Khan Rao, Moonis Ali Khan, Byong – Hun Jeon, 2010. Utilization of carbon derived from mustard oil cake (CMOC) for the removal of bivalent metal ions: Effect of anionic surfactant on the removal and recovery, Journal of Hazardous Materials 173 (1-3): 273-282.
- E.C. Bernardo, R. Egashira, J. Kawasaki, 1997. Decolorization of Molasses' Wastewater using Activated Carbon Prepared from Cane Bagasse, Carbon 35 (9): 1217-1221.
- Hui – Hsin Tseng, Jhin – Gang Su, Chenju Liang, 2011. Synthesis of granular activated carbon/zero valent iron composites for simultaneous adsorption/dechlorination of trichloroethylene, Journal of Hazardous Materials. 192 (2): 500-506.
- Jinchen Liu et al. 2007. Experimental and Theoretical Studies of Gas Adsorption in  $Cu_3(BTC)_2$ : An Effective Activation Procedure. J. Phys. Chem. C 111 (26): 9305-9313.
- Faisal I Khan, Alope Kr. Ghoshal, 2000. Removal of Volatile Organic Compounds from polluted air. Journal of loss prevention in the process industries, 13: 527-545.
- Antti Pasila, 2004. A biological oil adsorption filter. Marine pollution bulletin, 49 (11-12): 881-1128.
- Emine Yagmur, Meryem Ozmak, Zeki Aktas, 2008. A novel method for production of activated carbon from waste tea by chemical activation with microwave energy. Fuel, 87: 3278–3285.
- Tonghua Wang, Suxia Tan, Changhai Liang, 2009. Preparation and characterization of activated carbon from wood via microwave – induced  $ZnCl_2$  activation. Carbon. 47: 1867 – 1885.
- P. C. Sharma, M.B. Yelne, T.J. Dennis, 2001. Database on Medicinal Plants Used in Ayurveda, Central Council for Research in Ayurveda Siddha, New Delhi.
- Ozan Nazim Ciftci, Roman Przybylski, Magdalena Rudzinska, Surya Acharya, 2011. Characterization of Fenugreek (Trigonella foenum-graecum) Seed Lipids, J Am Oil Chem Soc. 88 (10): 1603–1610.
- Suchandra Chatterjee, Prasad S. Variyar, Arun Sharma, 2010. Bioactive lipid constituent of fenugreek. Food Chemistry. 119 (1): 349 – 353.
- Mullaicharam AR, Geetali Deori, and Uma Maheswari R, 2013. Medicinal Values of Fenugreek – A Review. RJPBCS 4 (1): 1304-1313.
- G.M.S. El. Bahy, 2005. FTIR and Raman Spectroscopic study of Fenugreek seeds. Journal of Applied Spectroscopy. 72 (1): 111-116.
- S. Aswathy Aromal, Daizy Philip. 2012. Green synthesis of gold nanoparticles using Trigonella foenum–graecum and its size-dependent catalytic activity. Spectrochimica Acta part A: Molecular and Biomolecular Spectroscopy. 97: 1-5.
- Maedeh Mohammadi, Ali J. Hassani, Abdul Rahman Mohamed and Ghasem D. Najafpur. 2010. Removal of Rhodamine B from aqueous solution using palm shell based activated carbon: Adsorption and kinetic studies. Journal of Chemical and Engineering Data. 55: 5777 – 5785.
- Y. C. Sharma, 2011. Adsorption characteristics of a low-cost activated carbon for the reclamation of coloured effluents containing malachite Green. Journal of Chemical and Engineering Data. 56: 478 – 484.
- K. Ramakrishnan, C. Namasivayam, 2011. Zinc chloride – activated jatropha husk carbon for removal of phenol from water by adsorption: equilibrium and kinetic studies. Toxicological & Environmental Chemistry 93(6): 1111 – 1122.
- Ravindra Kumar Gautam, Ackmez Mudhoo, Mahesh Chandra Chattopadhyaya, 2013. Kinetic, equilibrium, thermodynamic studies and spectroscopic analysis of Alizarin Red S by removal by mustard husk. Journal of environmental Chemical Engineering. 1: 1283-1291
- Eftekhari, S., Habibi – Yangjeh, A., Sohrabzhad, S., 2010. Application of AIMCM-41 for competitive adsorption of methylene blue and rhodamine B: Thermodynamic and Kinetic studies. Journal of Hazardous Materials. 178 (1-3): 349-355.
- Asma Saeed, Mehwish Sharif, Muhammad Iqbal, 2010. Application potential of grapefruit peel as dye adsorbent: Kinetics, equilibrium and mechanism of crystal violet adsorption, Journal of Hazardous Materials. 179: 564–572.
- Augustine E. Ofomaja, Yuh – Shan Ho, 2007. Equilibrium sorption of anionic dye from aqueous solution by palm kernel fibre as sorbent. Dyes and Pigments, 74: 60-66

28. Yu Liu, 2009. Is the Free Energy Change of Adsorption Correctly Calculated? Journal of Chemical and Engineering Data. 54: 1981 – 1985

29. Yu Liu, Hui Xu, 2007. Equilibrium, thermodynamics and mechanisms of Ni<sup>2+</sup> biosorption by aerobic granules, Biochemical Engineering Journal. 35: 174 – 182

---

**Persian Abstract**

---

*DOI: 10.5829/ijee.2017.08.03.03*

**چکیده**

در این مقاله، تهیه کربن فعال از تخم شنبلیله با استفاده از دو روش شیمیایی و میکروویو مودر مطالعه قرار گرفت. تعیین مشخصات محصول به وسیله FTIR، SEM، TGA و XRD به انجام رسید. آزمایش های جذب به منظور جذب دو رنگ بازی متیل بلو و کریستال ویوله تحت شرایط مختلف انجام شد. داده های بدست آمده از آزمایش به خوبی با لانگمویر و فرندلش همخوانی داشت.

---